


BORAL MATERIALS TECHNICAL SERVICES LABORATORY

CLIENT: Evenrange PTY. LTD.

FILE No.: 258/14

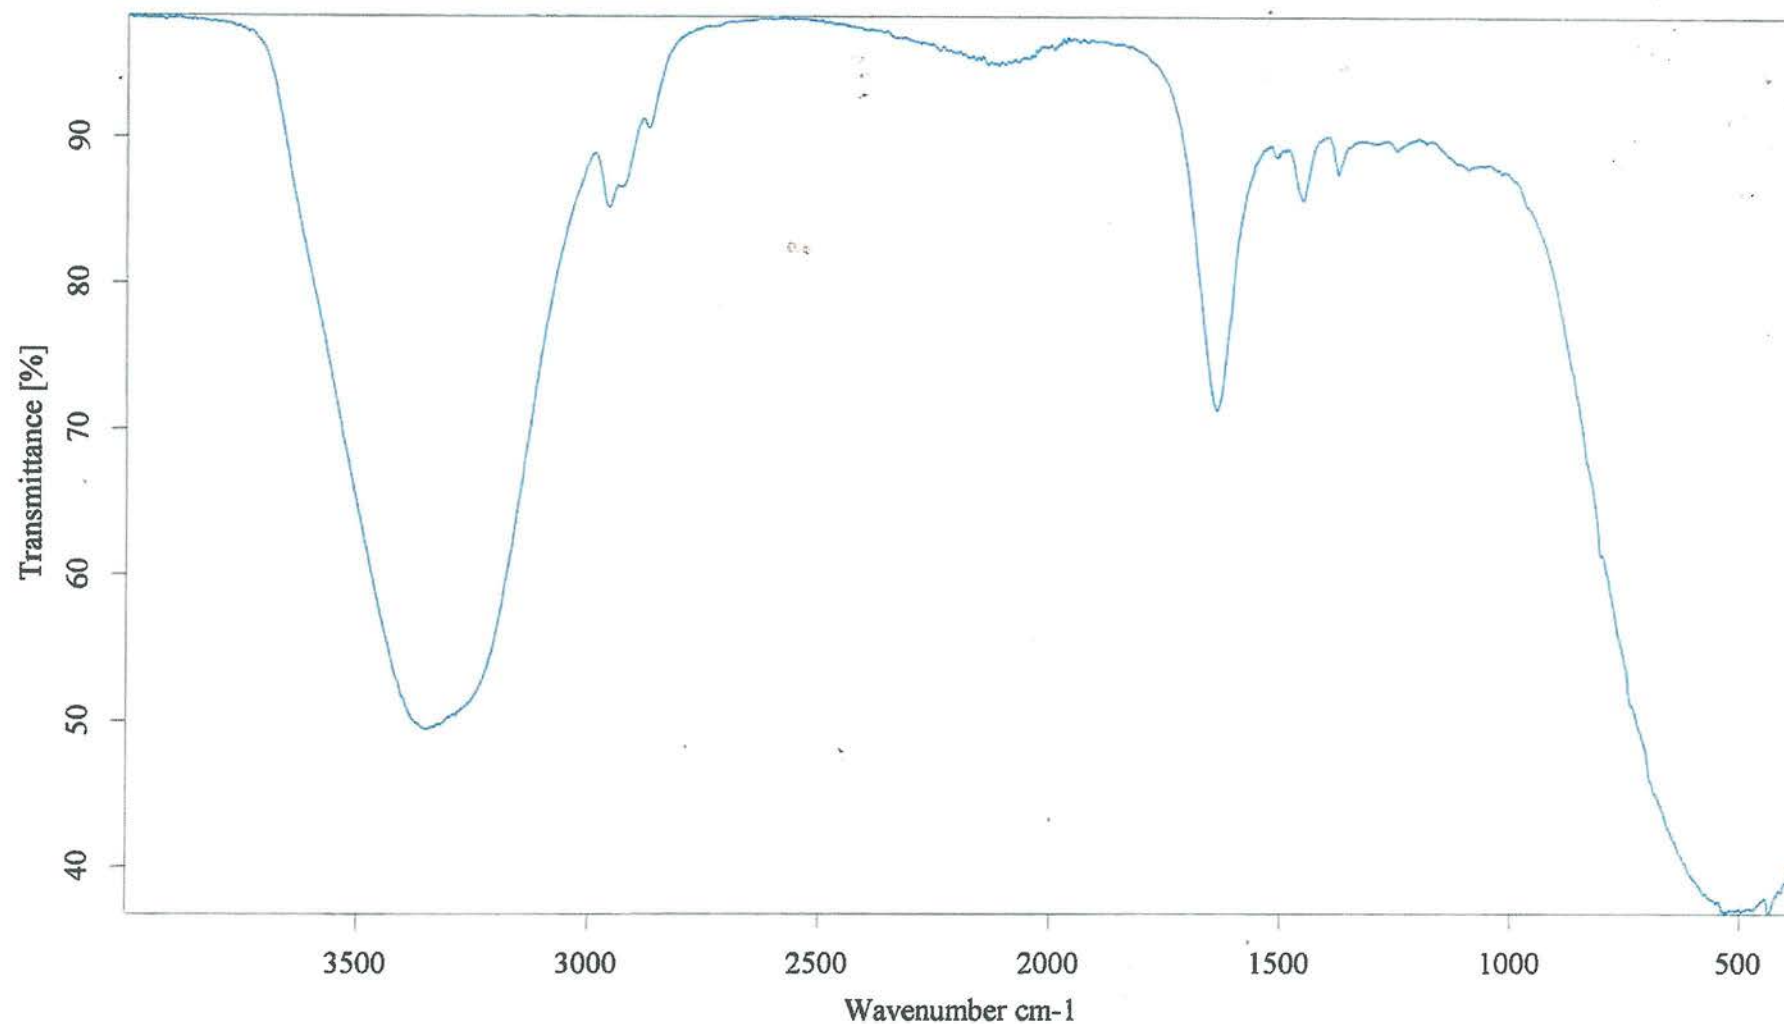

LSN 153837 Evencure XDS

Tested By: *Nallo*
Date: 20/05/14



TEST REPORT

File No: 258/09

Laboratory Sample No: 90372

Job description: CURING COMPOUND EVALUATION
Test Method: AS 3799 - 1998

CLIENT: EVENRANGE Pty Ltd

Sample identification: Evencure XDS
Sample Description: Blend of resins and surfactants emulsion in water.
Classification: Type 1, Class B

Source of sample: supplied by client
Date of sampling: Sept 2012 as supplied by client

TEST RESULTS:

Standard property, Test (Method)	Specification	Result
Non - volatile content AS 3799.3.1.8 (Method AS 1580.301.1/ RTA T865)	N / A	32.52%
Density AS 3799.3.1.9 (Method AS 1580.2002.1)	N / A	0.969
Water retention efficiency AS 3799.3.1.2 (Method AS 3799 Appendix B)	Min. 90%	91%
Viscosity AS 3799.3.1.5 (Method AS 1580.214.5)	Min. 0.05 Pa's	0.30 Pa's
Drying Time AS 3799.3.1.4 (Method AS 1160 Appendix C)	Max. 4 hrs	3 hrs
Stability of emulsion T 862 (RTA 3203)	Max 4%	3%
Infrared absorption spectrum AS 3799.3.2 (Boral Method)	N / A	attached
Residue 150µm AS 3799.3.1.6 (Method AS/NZS 2341.20)	Max. 0.2%	0.08%

The sample submitted and identified by the client - complies with the requirements of AS3799 - 1998 for the above listed properties.

Valentin Mukhin
Product Development Supervisor

Date: 2/9/2012